

Kiwa GmbH  
TBU  
Gutenbergstraße 29  
48268 Greven

Tel. +49 (0)2571 9872 0  
Fax +49 (0)2571 9872 99  
infokiwagreven@kiwa.de  
www.kiwa.de

## Test Report No. 1.1 / 13525 / 1048.0.1-2016e

### General

Issued : 28 February 2017

Order by : **Dörken GmbH & Co. KG**  
Wetterstr. 58  
58313 Herdecke/Ruhr, GERMANY

Material : Composite consisted of HDPE dimpled sheet (grey) and PP nonwoven (grey)  
**DELTA TERRAXX**  
(declaration by customer)

Order date : 02 September 2016

Samples delivered : 17 November 2015

Tests	Standard	Issue	Results as Enclosure No.
1. Compressive creep	DIN EN ISO 25619-1	06.2009	A1

The results apply exclusively to the specimens submitted.  
The date of testing is reported on the enclosed enclosure/-es.  
Results are reported to the accuracy given in the standards. In statistical evaluation, the measured accuracy is taken.

This test report contains 2 pages and 1 enclosure/-es (enclosure/-es A1 ).  
It may not be published in parts.

**Test Report No. 1.1/13525/1048.0.1-2016e page 2**


**Summary of results**


Date / Ref. : 28 February 2017 / mk


Order by : Dörken GmbH & Co. KG, Wetterstr. 58, 58313 Herdecke/Ruhr, GERMANY

Material : Composite consisted of HDPE dimpled sheet (grey) and PP nonwoven (grey)  
**DELTA TERRAXX**  
(declaration by customer)

Test	Standard	Unit	Result
<b>Compressive creep</b>	DIN EN ISO 25619-1 06.2009		
Normal stress 100 kPa			
Shear stress -			
Specimen 1			
Thickness after 1 h stress		mm	8,61
Thickness after 1006 h stress		mm	8,38
Specimen 2			
Thickness after 1 h stress		mm	8,64
Thickness after 1006 h stress	mm	8,42	

  
i.V. Matthias Käsekamp, B. Eng.  
(Deputy head of test laboratory)

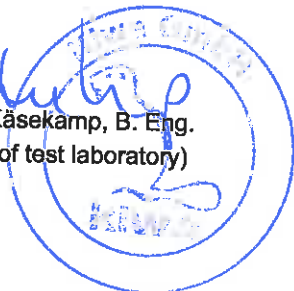

  
i.A. Friederike Schmale  
(Physiklaborantin, staff of test laboratory)



**Determination of the compressive creep properties DIN EN ISO 25619-1 (06.2009)**

Test Report No. : 1.1/13525/1048.0.1-2016  
 Company : Dörken GmbH & Co. KG  
 Material : DELTA TERRAXX  
 Operator : br

**Test parameters**

Normal stress : 100 kPa  
 Shear stress : -  
 Shear direction : -  
 MD - machine direction, CMD - cross machine direction

Specimen 1		Specimen 2	
96,6	x	96,9	=
8,61		0,0094	m <sup>2</sup>
		8,64	

Specimen size [mm x mm] :  
 Thickness after 1 h [mm] :  
 Test temperature :  
 Remarks : Specimen with 25 dimples

**Results** Begin of the test: 16.01.2017

Specimen No.	Thickness mm	Displacement mm	Time [h]																
			0,017	0,033	0,067	0,13	0,25	0,5	1,0	2,0	4,0	9,7	22	46	94	166	335	671	1006
1	8,80	8,77	8,74	8,71	8,67	8,64	8,61	8,59	8,55	8,52	8,49	8,47	8,45	8,43	8,41	8,39	8,38		
2	8,80	8,78	8,74	8,72	8,69	8,66	8,64	8,60	8,58	8,55	8,53	8,50	8,48	8,47	8,45	8,43	8,42		

